arXiv:cond-mat/0307388v1 [cond-mat.supr-con] 16 Jul 2003

Anisotropies of the lower and upper critical fields in MgB$_2$ single crystals

L.Lyard[1], P.Szabó[1,2], T.Klein[1,3], J.Marcus[1], C.Marcenat[4], B.W.Kang[5], K.H.Kim[5], H.S.Lee[5] and S.I.Lee[5]
[1] *Laboratoire d'Etudes des Propriétés Electroniques des Solides, CNRS, B.P.166, 38042 Grenoble Cedex 9, France*
[2] *Centre of Low Temperature Physics IEP SAS & FS UPJŠ, Watsonova 47, 043 53 Košice, Slovakia*
[3] *Institut Universitaire de France and Université Joseph Fourier, B.P.53, 38041 Grenoble Cedex 9, France*
[4] *Commissariat à l'Energie Atomique - Grenoble, Département de Recherche Fondamentale sur la Matière Condensée, SPSMS, 17 rue des Martyrs, 38054 Grenoble Cedex 9, France*
[5] *NVCRICS and department of Physics, Pohang University of Science and Technology, Pohang 790-784 Republic of korea*
(February 2, 2008)

The temperature dependence of the London penetration depth (λ) and coherence length (ξ) has been deduced from Hall probe magnetization measurements in high quality MgB$_2$ single crystals in the two main crystallographic directions. We show that, in contrast to conventional superconductors, MgB$_2$ is characterized by two different anisotropy parameters ($\Gamma_\lambda = \lambda_c/\lambda_{ab}$ and $\Gamma_\xi = \xi_{ab}/\xi_c$) which strongly differ at low temperature and merge at T_c. These results are in very good agreement with recent calculations in weakly coupled two bands suprerconductors (Phys. Rev. B, 66, 020509(R) (2002).

PACS numbers:74.25.OP, 74.25.Dw

The recent discovery of superconductivity in Magnesium Diboride [1] has been the starting point of a large number of theoretical and experimental investigations. The coexistence of two superconducting energy gaps with different anisotropies [2] is expected to give rise to very peculiar physical properties in this system [3–5]. Among those, the strong temperature dependence of the anisotropy of the upper critical field $\Gamma_{H_{c2}} = H_{c2\|ab}/H_{c2\|c}$ is now well established [6,7] ($H_{c2\|ab}$ and $H_{c2\|c}$ being the upper critical fields for magnetic fields parallel to the two main crystallograpic directions, $ab-$planes and $c-$direction, respectively).

"Classical" superconductors can be characterized by one single anisotropy parameter : $\Gamma = \xi_{ab}/\xi_c = \lambda_c/\lambda_{ab}$ (where ξ and λ are the superconducting coherence and penetration depths in signed crystallographic orientations) whatever the anisotropy of the superconducting gap. However, it has been suggested that ξ_{ab}/ξ_c could differ considerably from λ_c/λ_{ab} at low temperature in MgB$_2$ due to the presence of two superconducting energy gaps with different anisotropies [4]. Even though recent neutron scattering data have confirmed that $\lambda_c/\lambda_{ab} \sim 1$ at low temperature is indeed very different from $\xi_{ab}/\xi_c \sim 5$ [8], the temperature dependence of $\Gamma_\lambda = \lambda_c/\lambda_{ab}$ still had to be determined. In this letter, we confirm that $\Gamma_\xi = \xi_{ab}/\xi_c$ ($= \Gamma_{H_{c2}}$) strongly differs from Γ_λ at low temperature and show for the first time that Γ_ξ and Γ_λ present different temperature dependencies : whereas Γ_ξ decreases from ~ 5 to ~ 2 (close to T_c), Γ_λ increases with temperature tending from ~ 1.4 towards Γ_ξ for $T \to T_c$.

Magnetization measurements have been performed on high quality single crystal [9] ($T_c \approx 36.5$ K) showing flat surfaces of typical dimensions : $100 * 100 * 25\mu\text{m}^3$ using a Hall probe magnetometer. The main surface (i.e. the $ab-$planes) of the sample has been placed either parallel to or perpendicular to the surface of the Hall probes in order to measure the magnetization for $H\|c$ and $H\|ab$ respectively (see sketches in the inset of Fig.1a). The alignement of the external field with the main crystallographic axis has been obtained by slightly rotating the ensemble in order to get the maximum and mimimum H_{c2} values for $H\|ab$ and $H\|c$ respectively. A typical magnetization loop is presented in the inset of Fig1b for $H\|c$ and $T = 20$ K. As shown the irreversible part of the magnetization loops is rather small (corresponding to critical current values on the order of 10^3 A/cm^2 at low T and low H) and the reversible magnetization could thus easily be obtained assuming that $M_{rev} = (M_{up} + M_{down})/2$ where M_{up} and M_{down} are the magnetization for increasing and decreasing magnetic fields respectively (Bean critical state model). Typical curves are displayed in Fig.1 for $T > 26K$. For lower temperatures, the upper critical field values for $H\|ab$ became larger than our maximum field (3 T) but the lower critical field could still be deduced easily in both directions down to the lowest temperatures (5 K).

For $H\|c$ i.e. perpendicular to the platelet, important demagnetizing effect come into play and the magnetic field has been rescaled to : $H = H_0 - N_c M_{rev}$ where H_0 is the external field and N_c the demagnetizing factor. N_c can be estimated assuming that the sample is an ellipsoid of thickness $t \sim 25\mu$m and width $w \sim 100\mu$m to $N_c = 1 - \pi t/2w \approx 0.6$. This value has been confirmed by the fact that, after correction for this demagnetization effect, the magnetization curves present a nearly vertical slope for $H = H_{c1}$. As pointed out by Zeldov *et al.* [10] this value might however be overestimated by a factor on the order of $\sqrt{w/t}$ due to the presence of geometrical barriers but it is important to note that, even though the absolute values of $H_{c1\|c}$ - and $H_{c1\|ab}$ - are directly related to the choice of the demagnetizing factor, their temperature dependence is absolutely not affected by this choice.

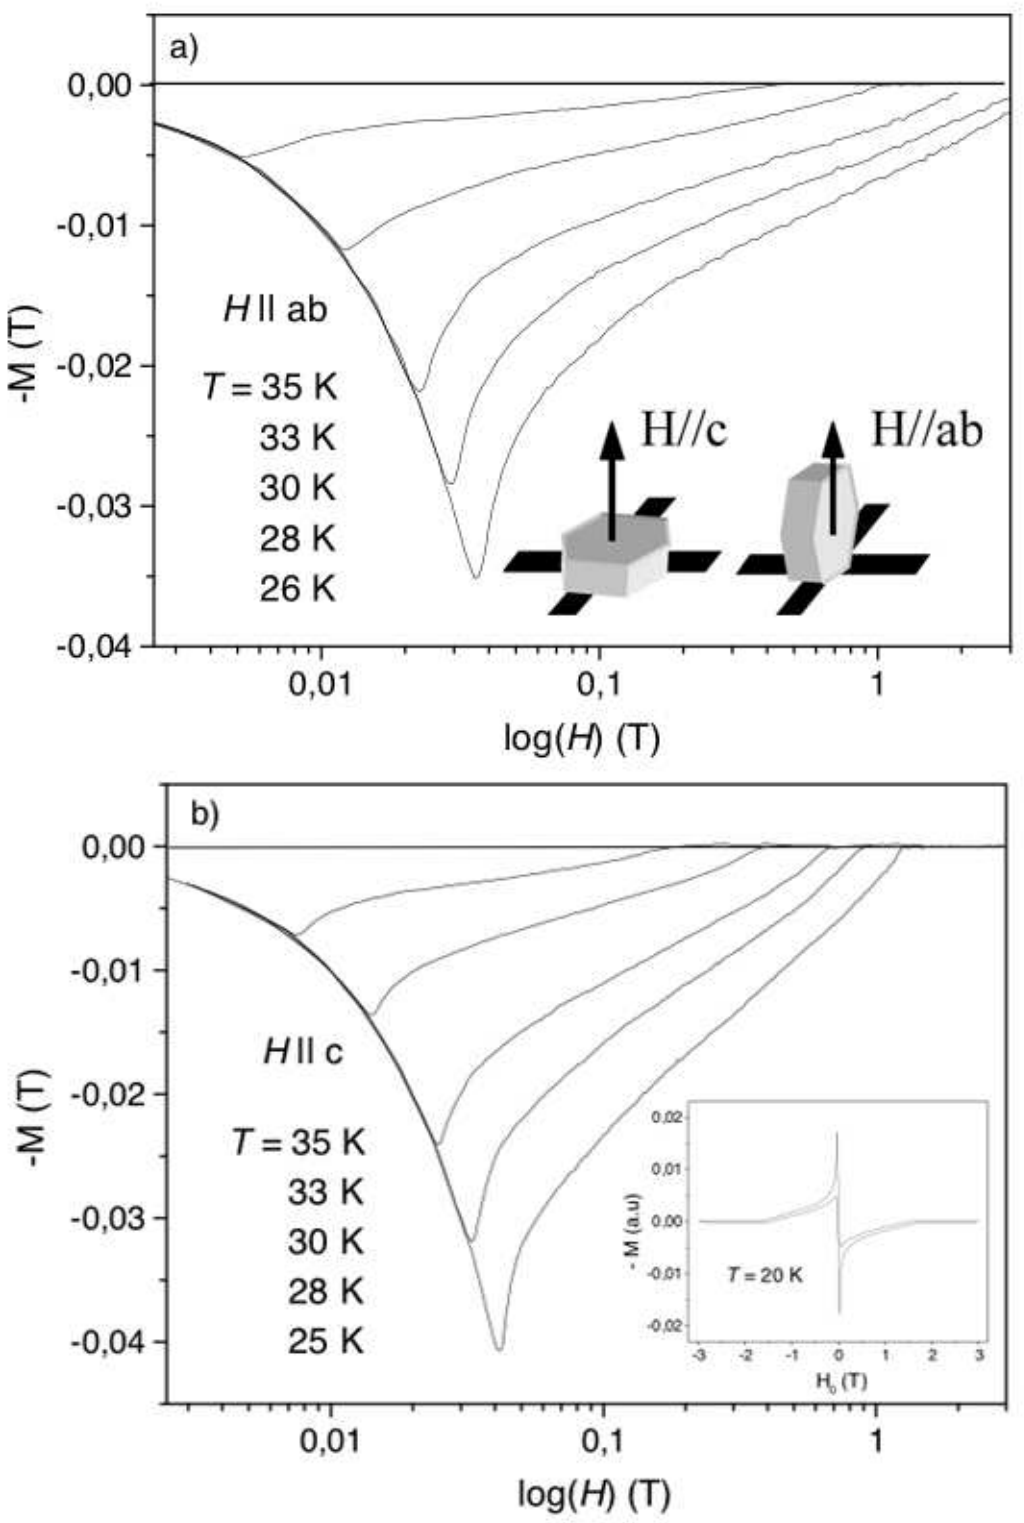

FIG. 1. Magnetic field dependence of the reversible magnetization for $H \| c$ (a) and $H \| ab$ (b) at various temperatures. In the inset : (a): schematical drawings of the geometry used for both directions, and (b): complete magnetization loop at $T = 20$ K for $H \| c$.

The value of N_{ab} has then been set to $N_{ab} \approx 1 - N_c/2$. In this direction, the effect of Bean Livingston barriers can also lead to a significant overestimation of H_{c1} (up to a factor $\kappa / ln(\kappa)$ where κ is the Ginzburg -Landau parameter, the penetration field is then equal to the thermodynamic field instead of the lower critical field). Those effects play for instance a significant role in high T_c cuprates due to their very high κ values [11]. They result from the competiting effect between an attracting image force to the surface and a repulsive one arising from the interaction between the vortices and the shielding currents. This latter force is proportional to the magnetization and thus vanishes as $M \rightarrow 0$ for descending magnetic fields. When the field further decreases nothing prevents the vortices to leave the sample and M remains close to zero. This effect is highly sensitive to the quality of the surface and we did never observe this characteristic behaviour in our magnetization loops. On the contary the irreversible part of the magnetization remained small in the entire temperature range (being for instance on the order of 15% at 30 K) and we thus assumed that M_{rev} is equal to the average magnetization (i.e. that pinning mainly arises from bulk defects).

The corresponding M_{rev} versus H curves are displayed in Fig.1. Note that the y-axis has been slightly rescaled in order to get a -1 slope in the Meissner state due to the fact that the sample did not completely recover the surface of the Hall probe (especially for $H \| ab$). Assuming that the lower critical magnetic field is equal to the penetration field (i.e. neglecting durface pinning effects, see discussion above), H_{c1} could be easily determined from the well defined minima in the $M_{rev}(H)$ curves (see Fig.1). The upper critical magnetic field H_{c2} has been defined as the onset of the diamagnetic response at $M_{rev}(H_{c2}) = 0$.

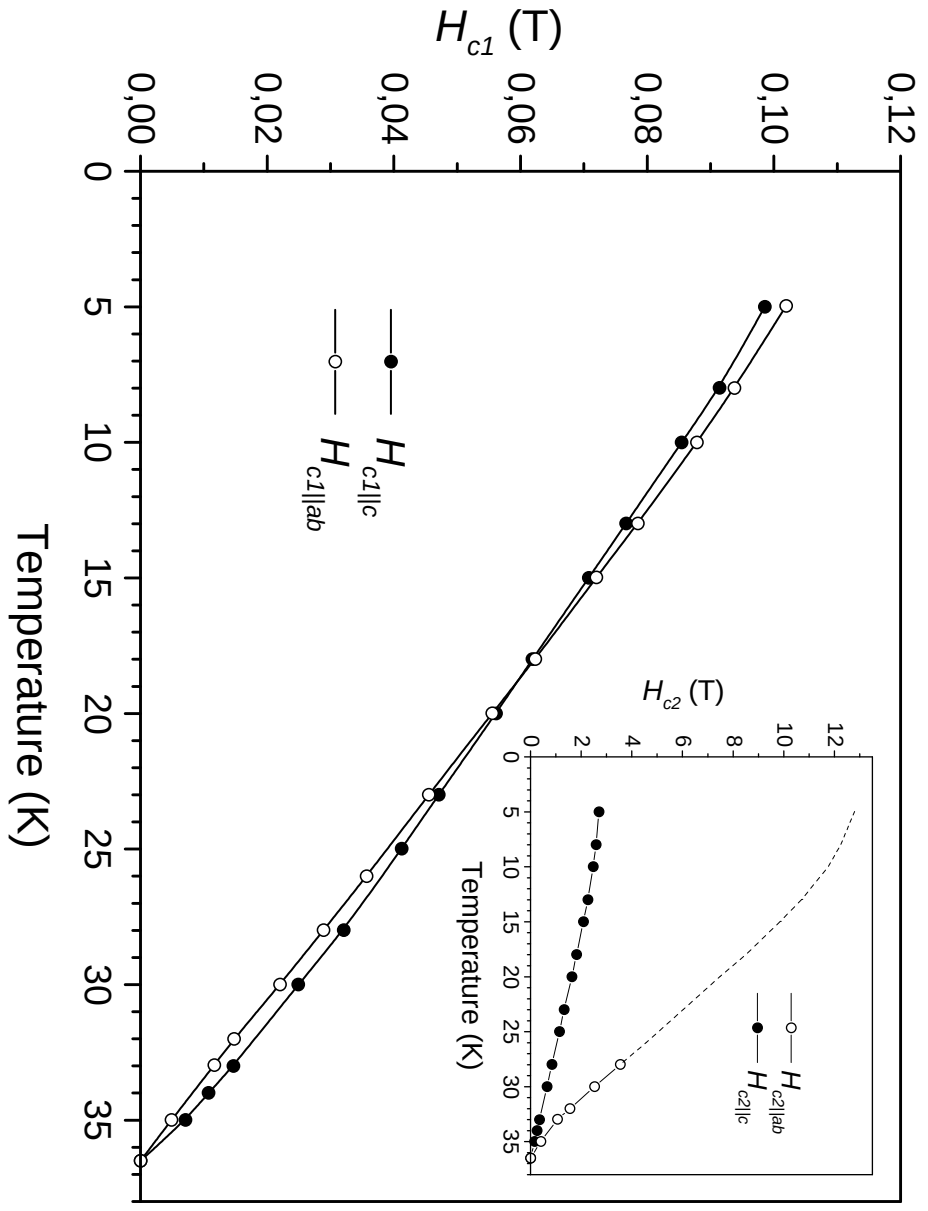

FIG. 2. Temperature dependence of the lower critical field for $H \| c$ and $H \| ab$. In the inset : Temperature dependence of the upper critical field for the same directions. The dotted line is an extrapolation below 26 K deduced from our previous magnetotransport measurements [5]

The temperature dependencies of the corresponding critical fields are displayed in Fig.2. The inset shows the temperature dependence of the upper critical magnetic field for $H \| c$ (solid circles) and $H \| ab$ (open circles) deduced from our magnetization measurements. Those values have been extrapolated down to low temperature for $H \| ab$ using our previous high field magneto-transport data performed on a sample from the same batch [6] (with slightly higher H_{c2} values, dotted line in the inset of Fig.2). As previously observed [6,7], the temperature dependence of H_{c2} is almost linear for $H \| c$ and presents a positive curvature for $H \| ab$. As shown, the situation is very different for the lower critical field which is almost linear for $H \| ab$ and reveals a *negative* curvature for $H \| c$ at high temperatures. This unusual negative curvature of $H_{c1\|c}$ close to T_c has been previously observed in thin films and polycrystalline samples [12] and can be explained by the two-band Ginzburg-Landau theory [13] (the isotropic Ginzburg-Landau theory only allows for a linear temperature dependence of H_{c1} close to T_c [14]). As shown below, this difference in curvatures will lead to an increase of Γ_λ for increasing temperature.

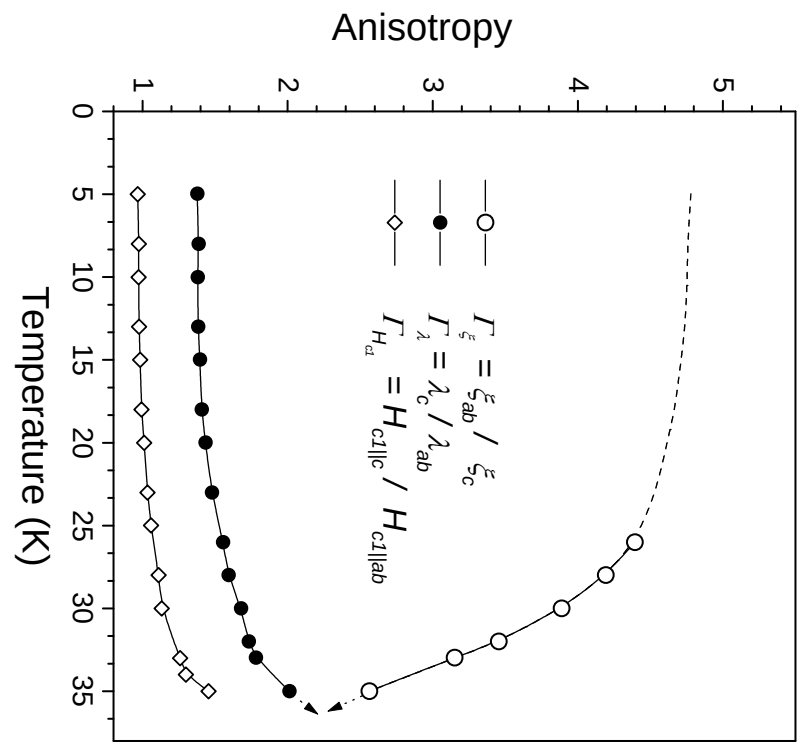

FIG. 3. Temperature dependence of the anisotropy parameters Γ_ξ, Γ_λ and $\Gamma_{H_{c1}}$ (see text for details). The dotted line is an extrapolation of Γ_ξ at low temperature deduced from our previous magnetotransport measurements [5].

The penetration depth has been deduced from H_{c1} through :

$$H_{c1} = \Phi_0/(2\pi\lambda_{ab}^2).(\Gamma_H/\Gamma_\lambda).(ln(\tilde{\kappa}) + 0.5) \qquad (1)$$

with $\tilde{\kappa} = \lambda_{ab}/\xi_{ab}$, $\Gamma_H = \Gamma_\lambda$ for $H \| c$ and $\tilde{\kappa} \approx \sqrt{\lambda_{ab}\lambda_c/\xi_{ab}\xi_c}$, $\Gamma_H = 1$ for $H \| ab$. The values of the coherence lengths $\xi_c(0) \approx 5$ nm and $\xi_{ab}(0) \approx 10$ nm have been determined from $H_{c2}(T)$ and we hence got $\lambda_c(0) \approx 80$ nm and $\lambda_{ab}(0) \approx 60$ nm in good agreement with the values deduced from the slope of the magnetization curve : $1/\lambda^2 = [8\pi/\Phi_0] d(\mu_0 M_{rev})/dln(H)$. Note that this slope rapidly decreases with field up to some characteristic field $H^*(T)$ being on the order of 0.3 T at low temperature. This field can probably be associated with the closing of the small gap, $H^* \sim H_{c2}^\pi$ in good agreement with our previous point-contact spectroscopy experiment [15] and with estimation of Bouquet *et al.* [16] from specific heat measurements and Eskildsen *et al.* [17] from tunneling data. Note that it has been suggested that for uniaxial superconductors $\tilde{\kappa}$ could be approximated to λ_{ab}/λ_c for all field directions [18] which would lead to $\lambda_c \approx \lambda_{ab} \sim 60$ nm.

The $\lambda_{ab}(0)$ value determined in this experiment is much larger than the one previously obtained on single crystals by Caplin *et al.* [19] but lower than those obtained on thin films and polycrystalline sampes [20,21,12]. However, λ is expected to be very sensitive to interband scatering and it has been shown [22] that $\lambda_{ab}^{dirty}(0) \approx 100$ nm whereas $\lambda_{ab}^{clean}(0) \approx 40$ nm (and $\lambda_c^{dirty}(0) \approx 300$ nm and $\lambda_c^{clean}(0) \approx 40$ nm) suggesting that our single crystals are close to the clean limit as further confirmed by our Γ_λ value ≈ 1.4 ($\Gamma_\lambda^{clean}(0) \sim 1$ and $\Gamma_\lambda^{dirty}(0) \sim 3$). This ratio is also in good agreement with the one recently deduced from neutron scattering measurements [8].

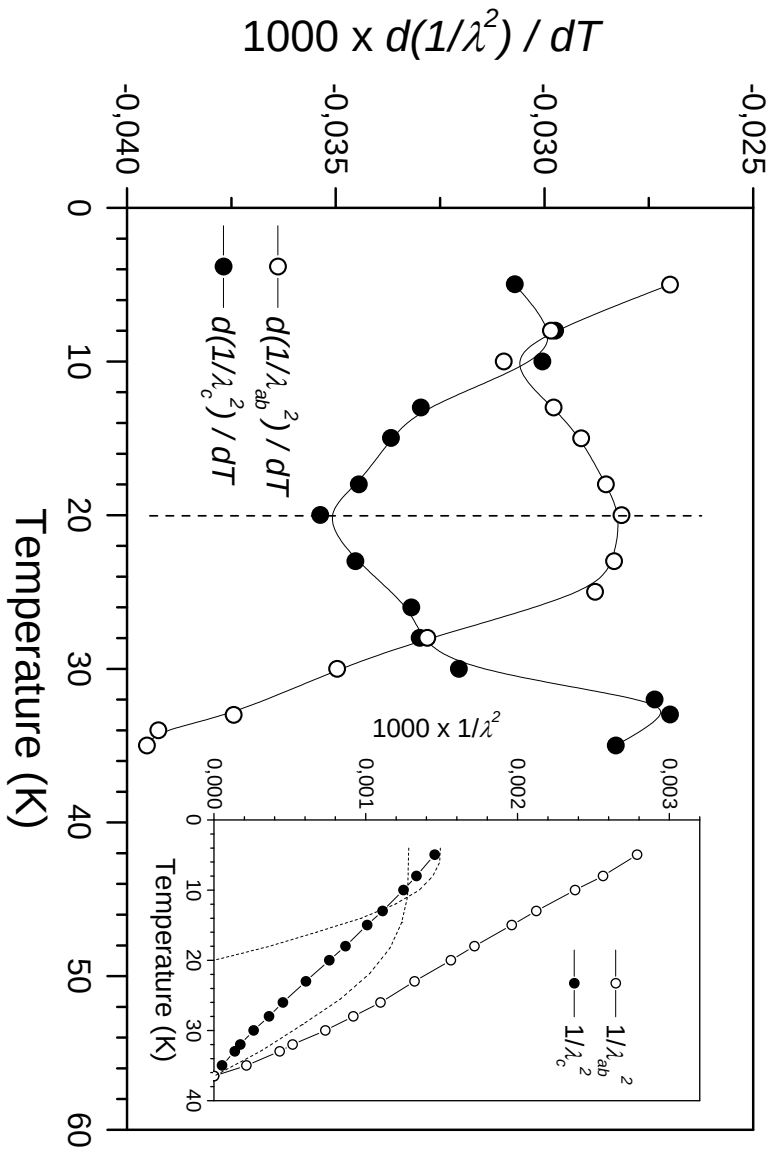

FIG. 4. Temperature dependence of $d(1/\lambda^2)/dT$ showing a maximum (resp. minimum) in the $ab-$planes (resp. $c-$direction). In the inset : temperature dependence of $1/\lambda^2$ for the two main crystallographic directions.

The temperature dependence of the as-deduced Γ_λ values is shown in Fig.3 as solid circles. $\Gamma_\xi(T)$ (open circles) has been deduced from our H_{c2} values above 26 K and extrapolated towards lower temperature using the $H_{c2}(T)$ extrapolation shown in the inset of Fig.2. As shown, in striking contrast with conventional one band superconductors the anisotropy parameters $\Gamma_\lambda(T)$ and $\Gamma_\xi(T)$ are very different at low temperatures. Moreover, they reveal opposite temperature dependencies and $\Gamma_\lambda(T)$ increases tending towards $\Gamma_\xi(T)$ for $T \rightarrow T_c$ where both anisotropies merges at $\Gamma_\xi(T_c) = \Gamma_\lambda(T_c) \sim 2$. This unusual behavior is also in striking contrast with the one previously obtained by Caplin *et al.* [19] who suggested that $\Gamma_\xi = \Gamma_\lambda \sim 2$ in the entire temperature range but is in a very good agreement with Kogan's [4] calculations of the anisotropy parameters for a weakly-coupled two-bands superconductor.

At low temperature the anisotropy of the upper critical field is mainly related to the anisotropy of the Fermi velocities *over the quasi 2D σ sheet* : $\Gamma_\xi \approx \sqrt{<v_{ab}^2>^\sigma / <v_c^2>^\sigma} \sim 6$. Γ_ξ then decreases with temperature as the influence of the small, nearly isotropic, gap increases due to thermal mixing of the two gaps [4,5]. On the other hand, the anisotropy of λ is related to the anisotropy of the Fermi velocities *over the whole Fermi surface* which is expected to be on the order of 1.1 in reasonable agreement with our experimental data. As pointed out by Kogan *et al.* [4] the two anisotropies have to merge at T_c as they are then determined by the same "mass tensor". We have also reported in Fig.3 the temperature dependence of $\Gamma_{H_{c1}} = H_{c1\|c}/H_{c1\|ab}$. As shown $\Gamma_{H_{c1}}$ and Γ_λ present very similar temperature dependencies (and only differ by a numerical factor on the order of 1.4) showing this dependence does not depend on the choice of $\tilde{\kappa}$ in Eq.(1).

Finally we discuss the temperature dependence of the superfluid density $\propto 1/\lambda^2$. The inset of Fig.4 displays $(\lambda(0)/\lambda(T))^2$ as a function of temperature for the two main crystallographic directions. The dotted lines schematically represents the temperature dependencies of the superfluid densities in the case of two independent BCS superconducting π (for which T_c would be on the order of 20 K) and σ bands. At low temperatures, the $T-$dependence of $1/\lambda_c^2$ and $1/\lambda_{ab}^2$ are both determined by the the band with the smallest gap (i.e. the $\pi-$band) and Γ_λ is only very weakly temperature dependent. As the temperature increases, the influence of the $\sigma-$ band sets in and an inflexion point is then clearly visible around 20K for $1/\lambda_{ab}^2(T)$ (see maximum for $d(1/\lambda_{ab}^2)/dT$ in Fig.4) followed by a downward curvature up to T_c. As pointed out in [22], this inflexion point is a direct consequence of the "superposition" of two BCS bands. The sharp kink that would appear for two independent bands is here smoothed out by interband coupling but still shows up as a clear maximum in the first derivative close to the "critical temperature" of the $\pi-$band. A very similar behaviour has been previously reported by Carrington *et al.* [21] for the superfluid density deduced from microwave measurements.

It is important to note that this change in the curvature at $T = 20$ K is also visible for $1/\lambda_c^2$ (see mimimum for $d(1/\lambda_c^2)/dT$ in Fig.4). In this direction, the penetration depth is mainly determined by the $\pi-$band up to T_c (in the clean limit) due to the very small value of the superfluid density of the $\sigma-$band (i.e. strongly 2D character of the $\sigma-$ band). Despite the small value of the corresponding gap, superconductivity remains induced in the π band by interband coupling giving rise to the "tail" of $1/\lambda_c^2$ at high temperature which shows up as a lower $d(1/\lambda_c^2)/dT$ value. Those temperature dependencies are qualitatively in good agreement with the recent calculations by Golubov *et al.* [22]. However, the details of those dependencies strongly depend on intraband scattering as well as on the relative contributions of the two bands.

In conclusion, we have given direct experimental evidence that the anisotropy of MgB_2 is characterized by two different parameters (Γ_λ and Γ_ξ) which differs not only in absolute values but also in their temperature dependencies in striking contrast to conventional type II superconductors. The as-deduced temperature dependencies of those two anisotropy parameters are in perfect agreement with theoretical predictions for weakly coupled two bands superconductor [4]. The presence of two different bands is enforced by the inflexion point observed around 20 K in the temperature dependence of $1/\lambda^2$ in both crystallographic directions.

The work of P.Sz. was partially supported by the Slovak Science and Technology Assistance Agency under contract No.APVT-51-020102. This work in Korea was supported by the Ministry of Science and Technology of Korea through the Creative Research Initiative Program.

---

[1] J. Nagamatsu et al., Nature **410**,63 (2001).

[2] P. Szabó et al., Phys. Rev. Lett. **87**, 137005 (2001), F.Giubileo et al. Phys. Rev. Lett. **87**, 177008 (2001), F.Bouquet et al. Europhys. Lett. **56**, 856 (2001).

[3] A. Y. Liu et al., Phys. Rev. Lett. **87**, 087005 (2001).

[4] V.G.Kogan, Phys. Rev. B **66** 020509(R) (2002); P. Miranovic et al. J. Phys. Soc. Jpn. **72** 221 (2003).

[5] T.Dahm and N.Schopol, Phys. Rev. Lett. **91** 017001 (2003).

[6] L. Lyard et al. Phys. Rev. B. **66**, 180502(R) (2002).

[7] S.L. Bud'ko et al. Phys. Rev. B **64**, 180506 (2001), M.Angst et al. Phys. Rev. Lett. **88**, 167004 (2002), U.Welp et al. Phys. Rev. B **67**, 012505 (2003).

[8] R.Cubitt et al. Phys. Rev. Lett. **90**, 157002 (2003).

[9] K.H.P.Kim et al. Phys. Rev. B **65**, 100510(R) (2002).

[10] E.Zeldov et al. Phys. Rev. Lett. **73**, 1428 (1994).

[11] M.konczykowski et al. Phys. Rev. B **43** , 13707 (1991).

[12] For a review see : C. Buzea et al. Supercond. Sci. Technol. **14** R115 (2001)

[13] I.N.Askerzade et al. Supercond. Sci. Techno. **15** L17 (2002)

[14] A.A.Abrikosov, in book *Fundamentals of the theory of metals*, North-Holland, Amsterdam (1988).

[15] P.Samuely et al. Physica C **385**, 154 (2003).

[16] F.Bouquet et al. Phys. Rev. Lett. **89**, 257001 (2002).

[17] M.R.Eskildsen et al. Phys. Rev. Lett. **89** 187003 (2002).

[18] A.B. Balatskii et al. Sov. Phys. JETP **63** 866 (1986).

[19] A.D.Caplin et al. Supercond. Sci. Technol. **16** 173 (2003).

[20] X.H.Chen et al. Phys. Rev. B **64**, 172501 (2001), C.Niedermayer et al. Phys. Rev. B **65** 094512 (2002).

[21] F.Manzano et al. Phys. Rev. Lett. **88** 047002 (2002), A.Carrington and F.Manzano, Physica C **385**, 205 (2003).

[22] A.A. Golubov at al. Phys. Rev. B. **66**, 054524 (2002).